

# Fascinating Improvement in Mechanical Properties of Cement Mortar using Multiwalled Carbon Nanotubes and Ferrite Nanoparticles

M.A. Ahmed<sup>1</sup>, Y.A. Hassanean<sup>2</sup> and K.A. Assaf<sup>3</sup>

<sup>1</sup> Cairo university

*Received: 13 June 2015 Accepted: 1 July 2015 Published: 15 July 2015*

---

## Abstract

The Mn-Ferrite nanoparticles were prepared using citrate nitrate auto combustion method. The Multiwalled carbon nanotubes (MWCNTs) and MnFe<sub>2</sub>O<sub>4</sub> nanoparticles were characterized by BET to measure the surface area. XRD data of MnFe<sub>2</sub>O<sub>4</sub> nanoparticles clarified that the sample was formed in single phase spinel structure without any extra peaks indicating any secondary phase. The High-resolution transmission electron microscopy (HRTEM) micrograph of MnFe<sub>2</sub>O<sub>4</sub> nanoparticles indicated that the particles are in an agglomerated state due to the absence of surfactant and high magnetic properties of Mn-Ferrite nanoparticles. Also, HRTEM micrograph showed that the walls of MWCNTs are straight having high crystallinity without any kinks. The mechanical properties were measured at different ratios of MWCNTs and nano-ferrite to cement. The obtained values indicated that the addition of MWCNTs and nano-ferrite increase the compressive and flexural strength of cement mortar and decrease the total intrusion volume.

---

*Index terms*— MWCNTs, MnFe<sub>2</sub>O<sub>4</sub> nanoparticles, HRTEM, compressive strength, flexural strength.

## 1 Introduction

concrete is one of the most prevalent materials on the ground and holds promises to be a cornerstone for our expansion in construction industry. More than 10 billion tons of it are produced every year for everything from major infrastructure projects like bridges, tunnels, dams, to homes, stadiums, and skyscrapers. However, cementitious materials in general, are very brittle and characterized by a very low tensile strength and strain capacity [1,2]. The mechanical property of concrete arises from a phenomenon that occurs at the micro and nano scale i.e. interlinking of dendrites of calcium silicate hydrates during the hardening process. Nanoscale binders can modify the structure of concrete material and enhance its properties including bulk density, mechanical performance, volume stability, durability and sustainability of concrete [3].

Within the last few years, an increasing interest is in the application of nanoparticles in concrete, because nanoparticles due to its high specific surface area and high activity offers the opportunity to improve the mechanical properties of concrete and enhance the Author ??: Materials Science lab. (1), physics Department, Faculty of science, Cairo University, Giza, Egypt. e-mail: moala47@hotmail.com Author ??: Department of civil engineering, Assiut University, Egypt.

understanding of concrete behavior [4]. CNTs and ferrite nanoparticles are quickly becoming one of the most promising nanomaterials because of their unique mechanical properties.

The superior mechanical properties of the CNTs and ferrite nanoparticles alone don't ensure the improvement of mechanical properties of cement. The properties of the concrete composite are strongly influenced by two major factors. The first is the dispersion of these nanomaterials within the cementitious matrix. The other is the bond strength and energy between the matrix and surface of the CNTs or ferrite nanoparticles [1].

Several researches have been done on the partial replacement of cement with supplementary nanomaterials to improve their mechanical properties. The most of these researches are focusing on using  $\text{SiO}_2$  [5] nanoparticles and CNTs [1]. There are a few studies on incorporating of different nanoparticles such as  $\text{Fe}_2\text{O}_3$  [6],  $\text{Al}_2\text{O}_3$  [7],  $\text{CaCO}_3$  [8],  $\text{TiO}_2$  [9],  $\text{ZnO}$  [10],  $\text{ZrO}_2$  [11] and  $\text{CuO}$  [12].

Sulapha Peethamparan et al. [5] discussed the effects of nano-silica (NS) on setting time and early strengths of high volume slag mortar and concrete. He used a constant water-to-cementitious materials ratio (w/cm) 0.45 for all mixtures. He found that compressive strength of the slag mortars increased with the increase in NS dosages from 0.5% to 2.0% by mass of cementitious materials at various ages up to 91 days.

M. Razzaghi et al. [13] added Nano- $\text{ZrO}_2$  (NZ), Nano- $\text{Fe}_3\text{O}_4$  (NF), Nano  $\text{TiO}_2$  (NT) and Nano- $\text{Al}_2\text{O}_3$  (NA) to concrete mixtures to investigate its mechanical properties and durability. Results of this study showed that nanoparticles can be very effective in improvement of both mechanical properties and durability of concrete. The results indicated that the Nano- $\text{Al}_2\text{O}_3$  is most effective nanoparticle of examined nanomaterials in improvement of mechanical properties of high performance concrete.

Zachary Grasley et al. [1] used carbon nanotubes and carbon nanofibers for enhancing the mechanical properties of cementitious materials. He added untreated CNTs and CNFs to cement matrix composites in concentrations of 0.1% and 0.2% by weight of cement. The flexural test was performed to  $\text{MnFe}_2\text{O}_4$  nanoparticles with average diameter of 49 nm and average surface area of 27.28  $\text{m}^2/\text{g}$  was prepared by citrate nitrate auto combustion method at materials science lab. (1) [15,16]. The properties of  $\text{MnFe}_2\text{O}_4$  nanoparticles are also shown in Table (2)

## 2 Materials and Methods

### 3 a) Materials and Mixtures i. Cement

Ordinary Portland Cement (OPC) grade (CEM I 52.5N) obtained from AL-Areash Cement Manufacturing Company of Egypt conforming to the British standard BS 12/1996 [14] was used as received. The chemical properties of the cement are obtained from Pnalytical Axios Advanced X-ray fluorescence (XRF) and the results are reported in Table (1).

record its mechanical properties at 7, 14, and 28 days. Nine Mixtures of cement mortar were prepared in the laboratory trials. These Mixtures included a reference sample of plain cement mortar, three mixtures of cement mortar with MWCNTs at 0.3 wt%, 0.5 wt% and 0.7wt% by weight of dry cement, three mixtures of cement mortar with  $\text{MnFe}_2\text{O}_4$  nanoparticles at 0.3 wt%, 0.5 wt% and 0.7wt% and two mixtures of cement mortar with both MWCNTs and  $\text{MnFe}_2\text{O}_4$  nanoparticles at 0.15 wt%, 0.3 wt% for each of them. Table (4) summarizes the composition of the nine mixtures.

The superplasticizer was dissolved in water, and then MWCNTs and  $\text{MnFe}_2\text{O}_4$  nanoparticles were added and good stirred at a high speed for 2 min. The binder content of all mixtures was 635  $\text{kg}/\text{m}^3$ . The total mixing time including homogenizing was 5 minutes.

### 4 b) Strength Evaluation Tests

Cubic Specimens with 50 mm edge length were used for compressive tests and prism specimens with dimensions 40 x 40 x 160 mm were used for flexural tests. The moulds were covered with polyethylene sheets and moistened for 24h. Then, the specimens were demoulded and cured in water at room temperature prior to test days [6]. The strength tests of the samples were determined after 2 and 14 days of curing. The tests were carried out triplicately and average strength values were obtained. MIP Poresizer 9320 V2.08 was used to characterize the pore structure in porous material as a result of its simplicity, quickness and wide measuring range of pore diameter [17,18]. MIP gives us details about the dimensions of pores [17]. To prepare the samples for MIP measurement, the concrete specimens after 14 days of curing were first broken into smaller pieces, and then the cement paste fragments selected from the center of prisms were used to measure pore structure. The samples were immersed in acetone to stop hydration as fast as possible. Before mercury intrusion test, the samples were dried in an oven at about 110° C until constant weight is obtained by removing moisture in the pores. MIP is based on the assumption that the non wetting liquid mercury (the contact angle between mercury and solid is greater than 90°) will only intrude in the pores of porous material under pressure [17,18]. Each pore size is quantitatively determined from the relationship between the volume of intruded mercury and the applied pressure [18]. The test apparatus used for pore structure measurement is Auto Pore III mercury porosimeter. The surface tension of mercury is taken as 485\*10<sup>-5</sup> N/cm (485 dyne/cm), and the contact angle selected is 130 deg. The maximum head pressure applied is (4.68 psi).

### 5 d) Field emission scanning electron microscope (FE-SEM)

After the samples had been tested, the fracture surface was cut into an approximately 1 × 1 × 0.5 mm. Then, a field emission scanning electron microscope (FE-SEM) (JSM-7500F, JEOL, Tokyo) was used to observe the fracture surface of the samples.

---

## 6 III.

## 7 Results and Discussion

Figs. (4)(5)(6)(7) show compressive and flexural strength of cement mortar specimens after 2 and 14 days of curing, respectively. The results show that the compressive and flexural strength increases by addition of MWCNTs content till 0.7 wt % replacements to cement mortar. This was due to the interfacial interactions between MWCNTs and cement hydrates to bridge nanocracks and pores to achieve good bonding with the cement hydration products.

On the other hand, by the addition of MnFe 2 O 4 nanoparticles with 0.5 wt%, the compressive and flexural strength increase after which it decreases. The reasons that allow MnFe 2 O 4 nanoparticles to increase the strength of concrete can be explained as follows. The addition of MnFe 2 O 4 nanoparticles reduces the quantity and size of Ca(OH) 2 crystals and fills the voids of Calcium Silicate Hydrate (C-S-H) gel structure. This makes the structure of hydrated products denser and compact [12]. Increasing MnFe 2 O 4 nanoparticles more than 0.5 wt%, the compressive strength reduces. This is because nanoparticles due to their high surface energy have the tendency towards agglomeration. When MnFe 2 O 4 nanoparticles are over added to the concrete, it is not uniformly distributed in cement paste and due to agglomeration, weak zones appear in the concrete specimen. The highest values of compressive and flexural strength achieved by the addition of both MWCNTs and MnFe 2 O 4 nanoparticles by 0.3 wt% for each of them with enhancement by 19 % for compressive strength and by 21% for flexural strength compared to the control specimen. This is due to the ability of MnFe 2 O 4 nanoparticles to fill the voids at the nanoscale and MWCNTs to act as bridges across voids and cracks that ensure more compact and durable cement mixture. The mercury intrusion results of the C0 specimen and N3-2 specimen are shown in Figs. (8,9). Fig. (8) represents the variation of incremental intrusion, reflecting pore volume against pore diameter, which indicates that most pore diameters of the specimen are distributed between 0.1 micrometer to 1 micrometer. Fig. (9) represents the cumulative intrusion, reflecting the total connected pore volume of pore sizes. Table (5) shows that by the addition of both MWCNTs and MnFe 2 O 4 nanoparticles by 0.3 wt% for each of them, total intrusion volume of specimens is decreased. This leads to decreasing total pore area and median pore diameter of cement mortar (area), but median pore diameter (volume) of these specimens is increased. On the other hand, Table (6) shows that the addition of MWCNTs and MnFe 2 O 4 nanoparticles leads to decreasing the porosity, increasing the average pore diameter and decreasing the bulk density and the apparent (skeletal) density of these specimens of cement mortar. This means that the regularity of porosity is similar to that of total intrusion volume and the regularity of average pore diameter is similar to median diameter (volume). The increase of average pore diameter and median diameter (volume) are due to the ability of MWCNTs and MnFe 2 O 4 nanoparticles. Figs. (10,11) present FE-SEM photographs of the cement mortar of C0 specimen and N3-2 specimen after 14 days of curing. The results confirmed an improved microstructure in the cement mortar with MWCNTs and MnFe 2 O 4 nanoparticles addition. In the control specimen shown in Fig. (10a, 11a), the microstructures were non-compact, with extensive presence of large crystals of calcium hydroxide. However, the voids among cement particles have been occupied by the hydration products, many connected capillary pores were observed.

The cement mortar specimen with MWCNTs and MnFe 2 O 4 nanoparticles addition showed denser formations of hydration products than the control specimen as shown in Fig. (10b, 11b). It is obvious that, regardless of the presence of many pores, the density is significantly improved and the volume of pores reduced due to the ability of MnFe 2 O 4 nanoparticles to fill the pores. This leads to improving impermeability thus the durability and the microstructure of the hardened cement-based materials [19]. The calcium hydroxide was observed as ill-crystals [20] IV.

## 8 Conclusions

The obtained results can be summarized as follows.

? The results showed that cement specimen reinforced with both MWCNTs and MnFe 2 O 4 nanoparticles after 7 and 28 days of curing have higher compressive and flexural strength compared to the control specimen.




Figure 1: Table 1 :

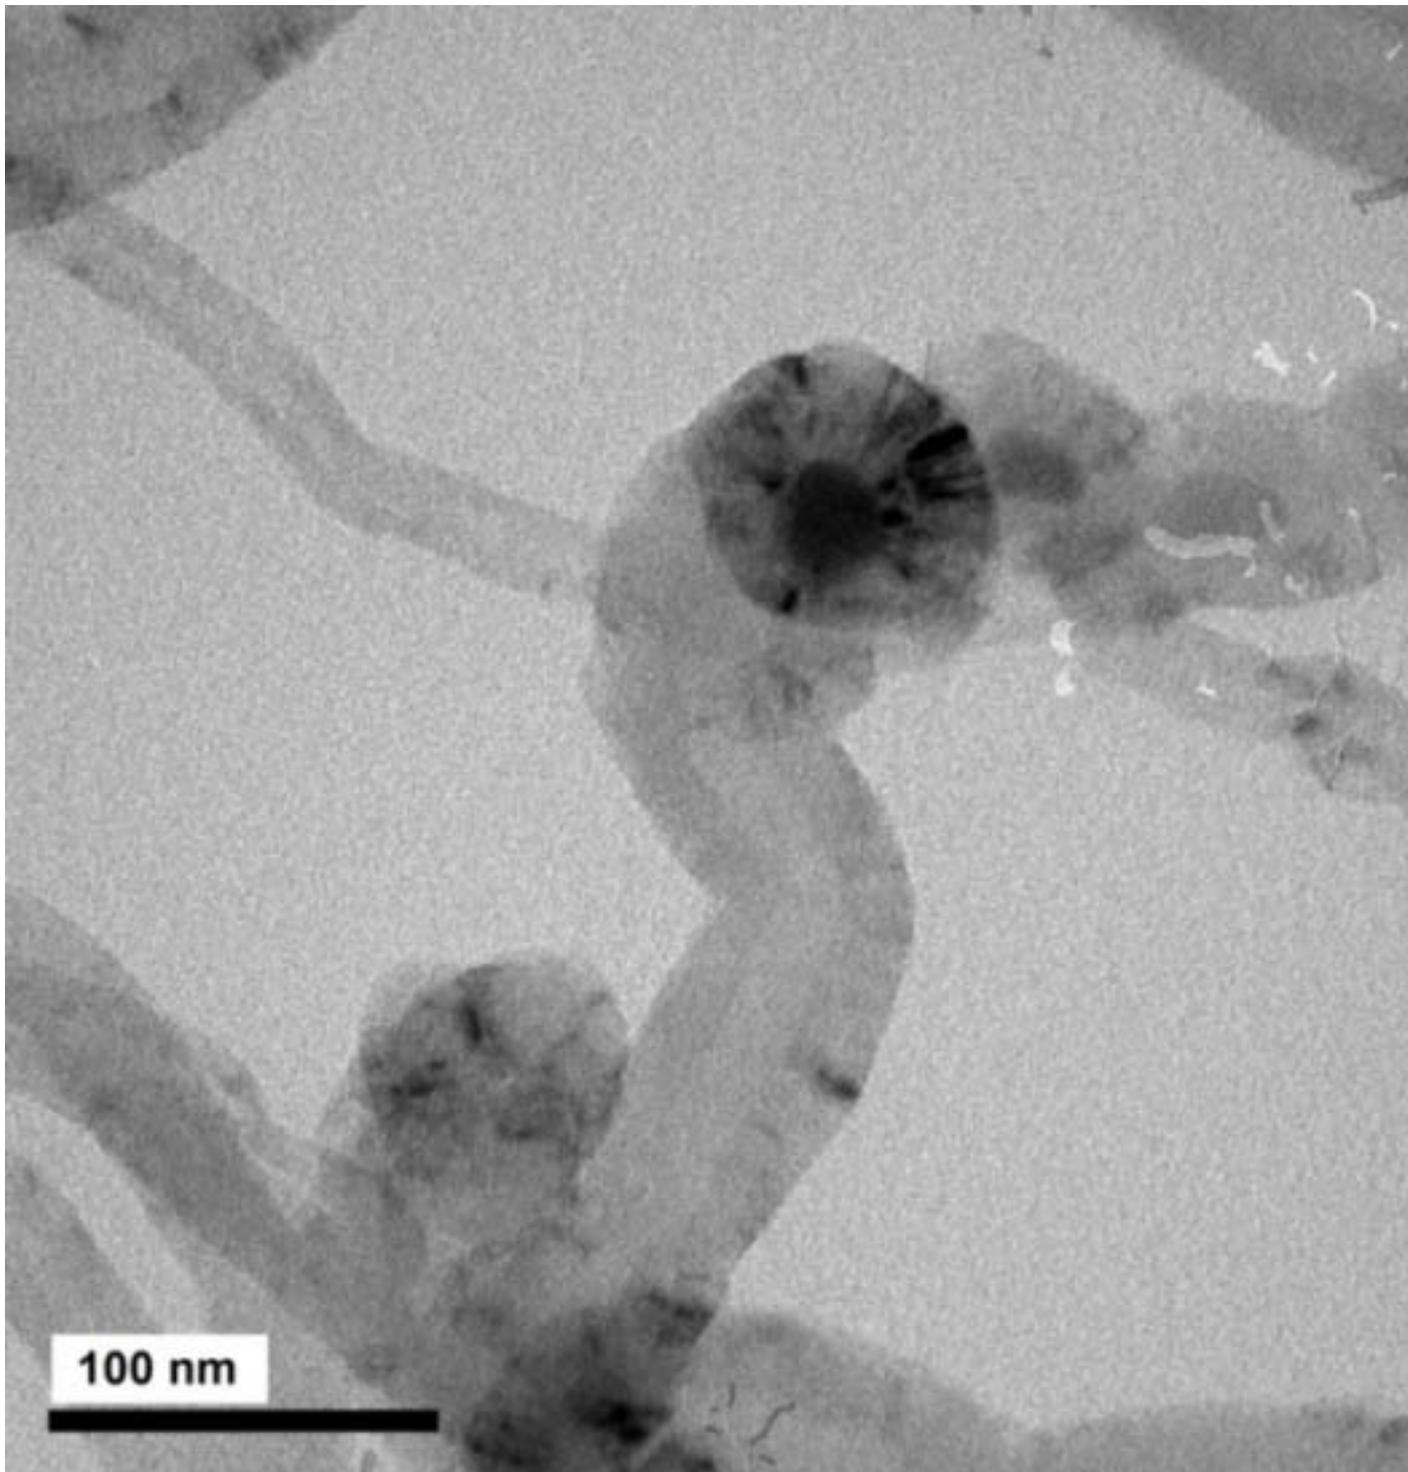


Figure 2:

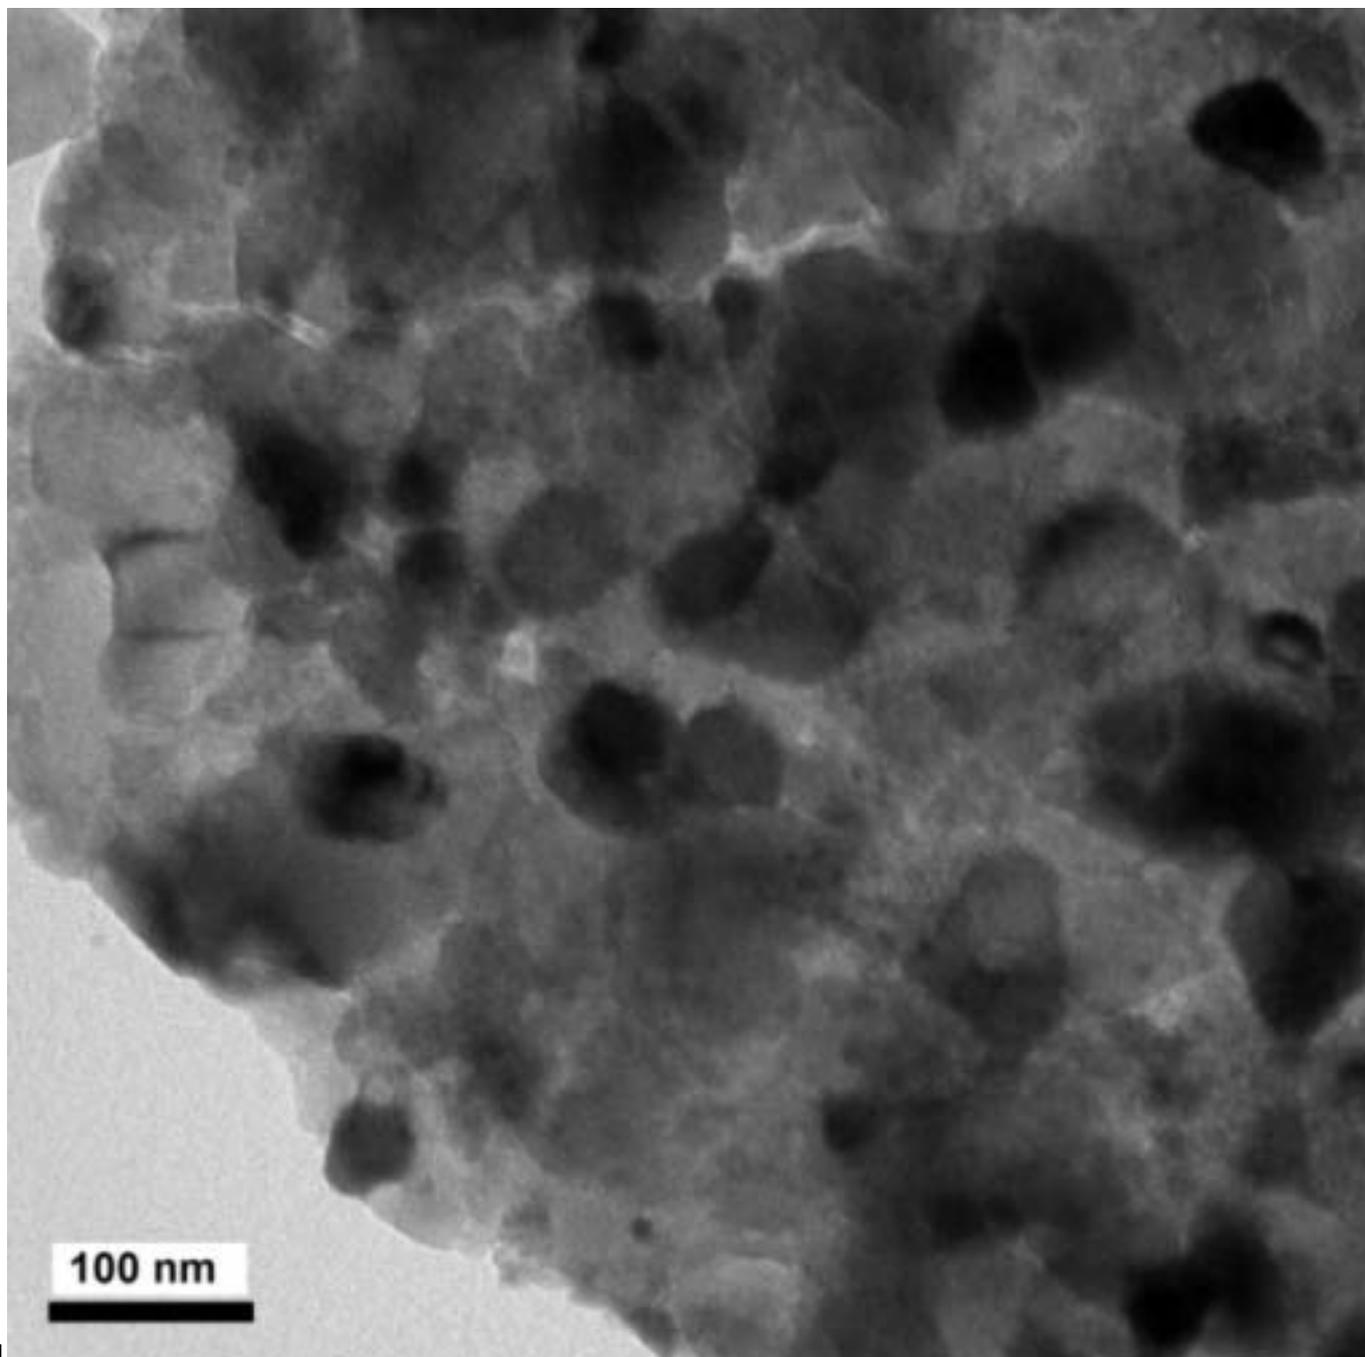


Figure 3: Fig. 1 :

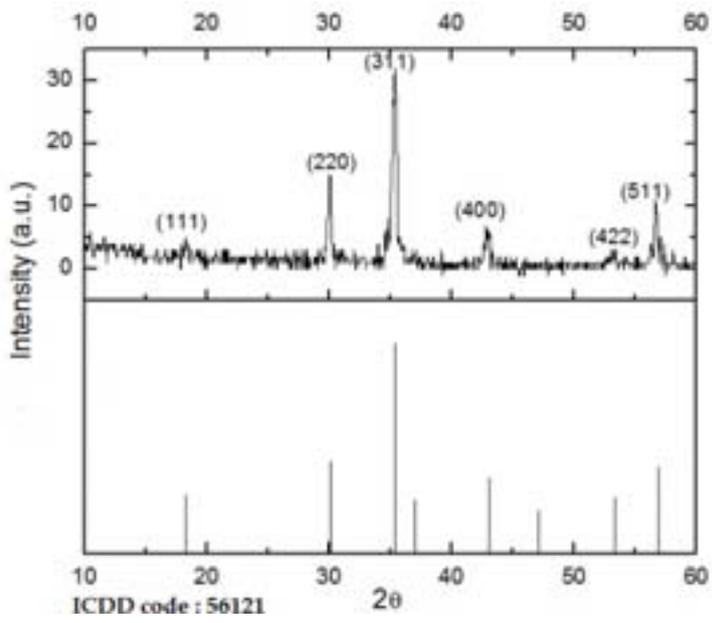


Figure 4:

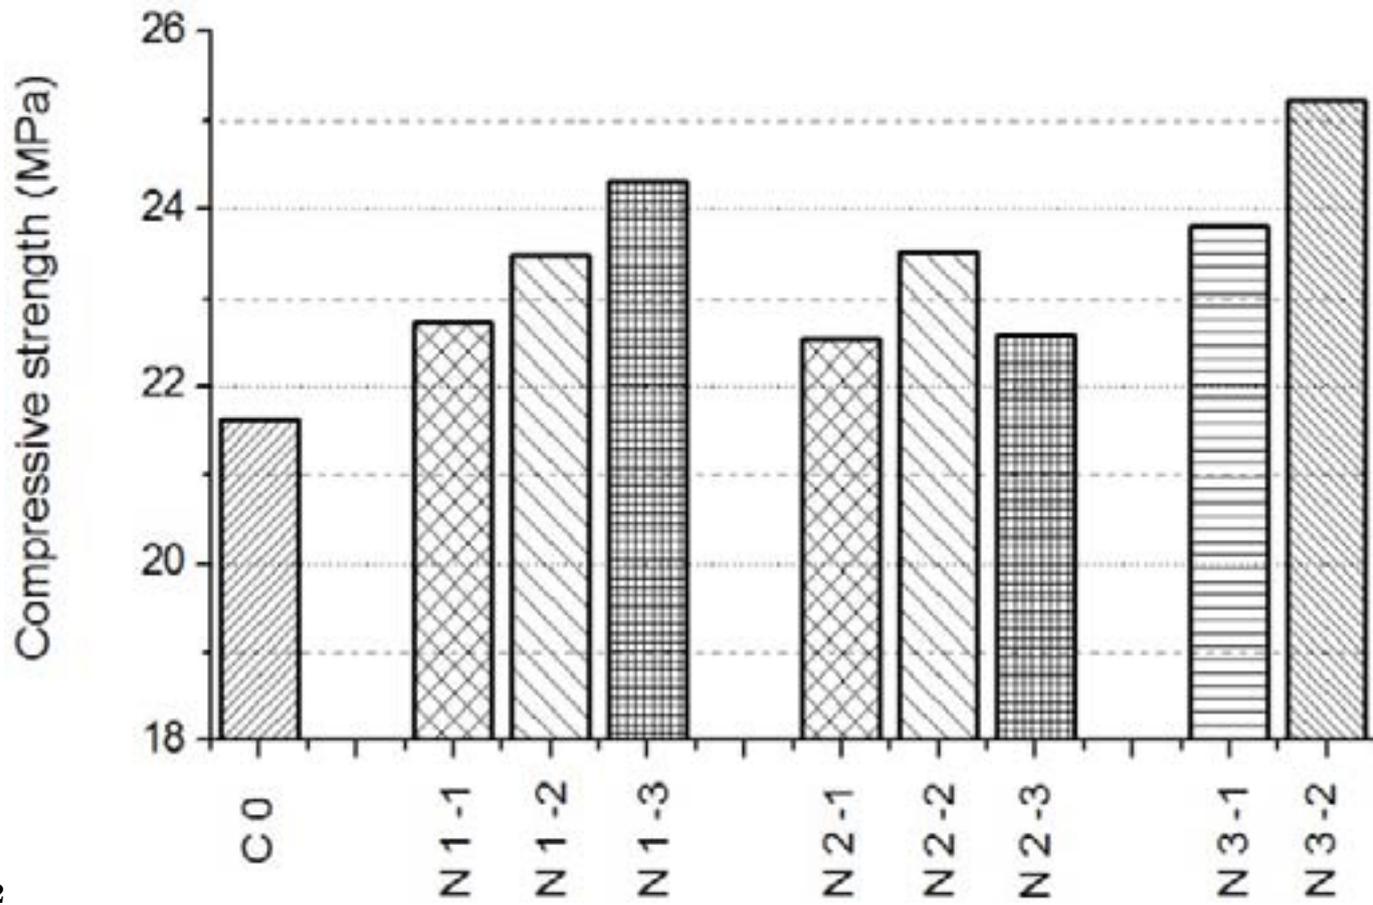


Figure 5: Fig. 2 :


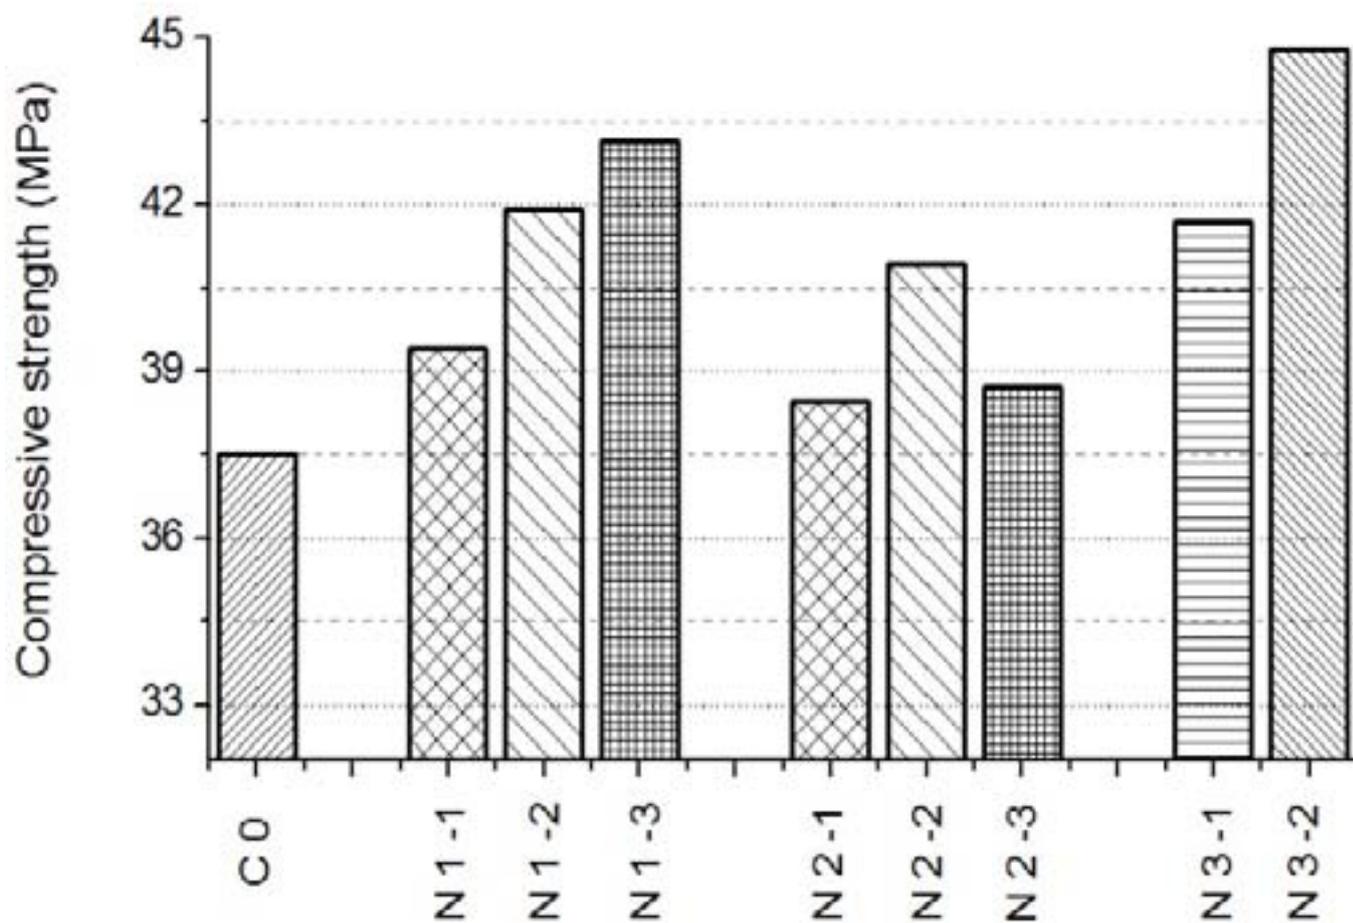


Figure 6: Fascinating

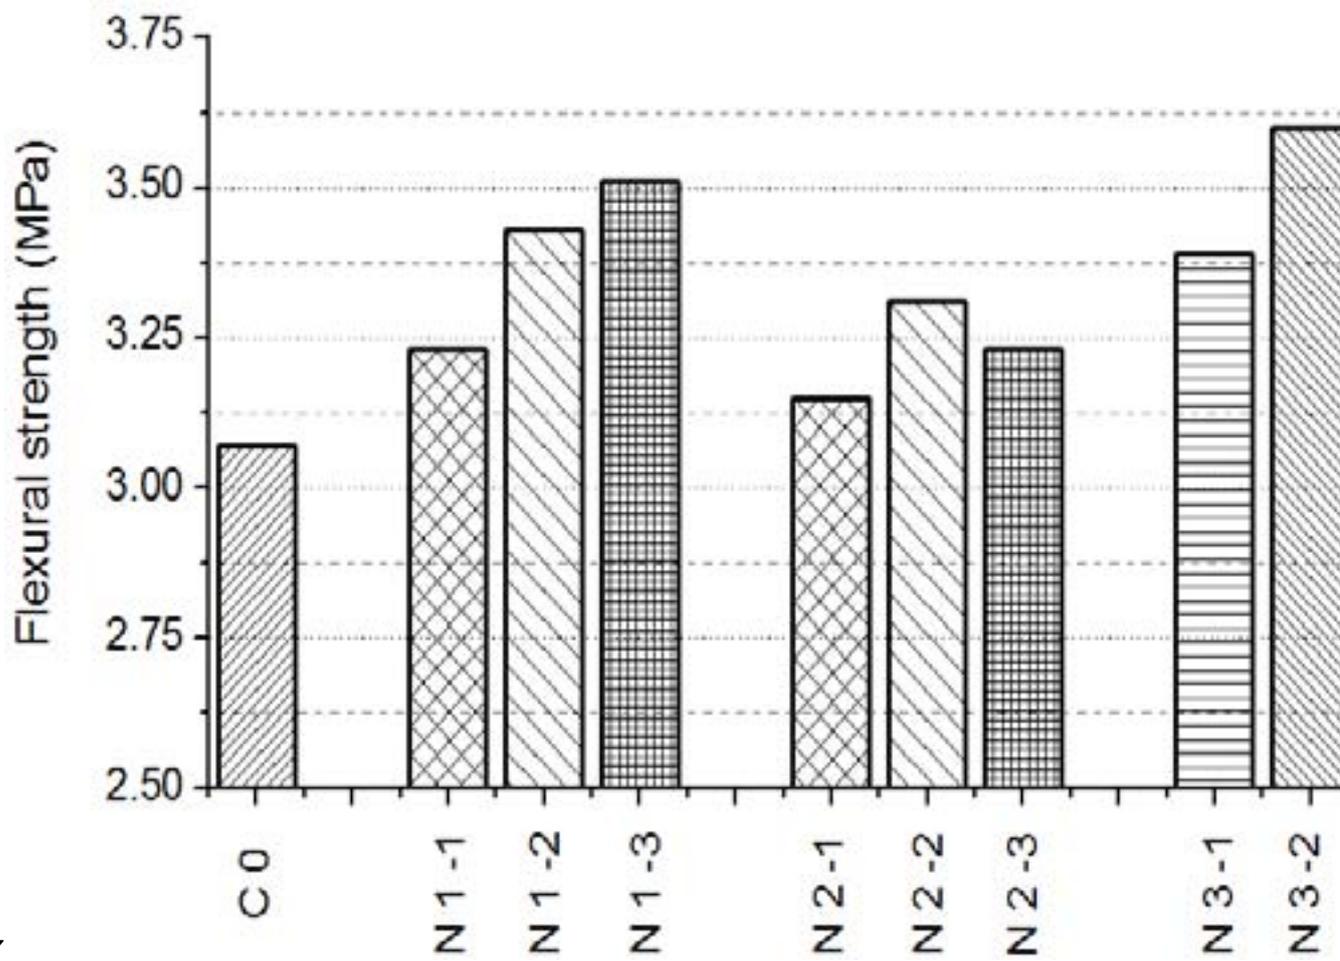

4567

Figure 7: Fig. 4 :Fig. 5 :Fig. 6 :Fig. 7 :


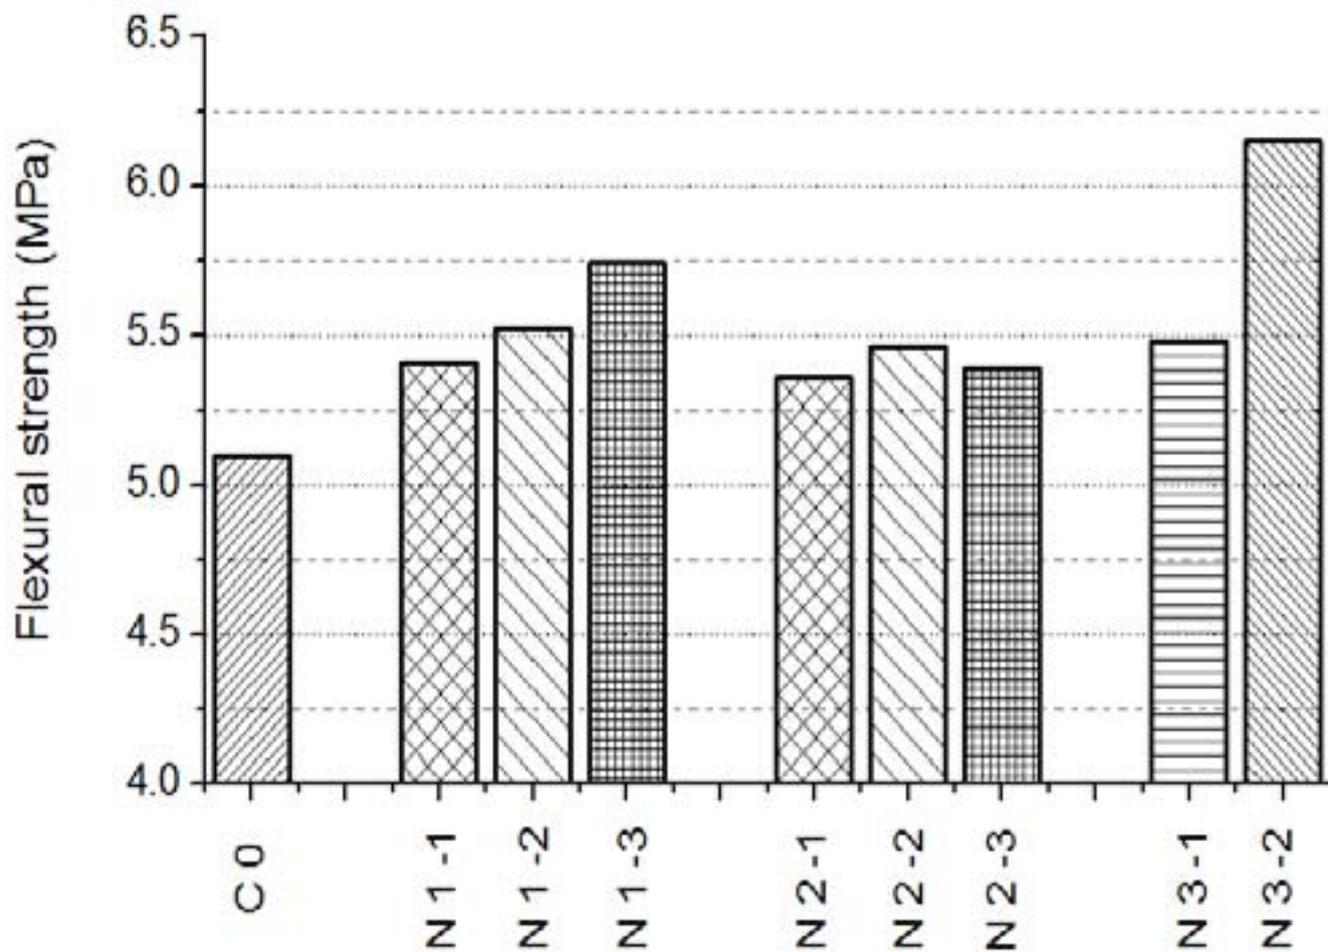


Figure 8:

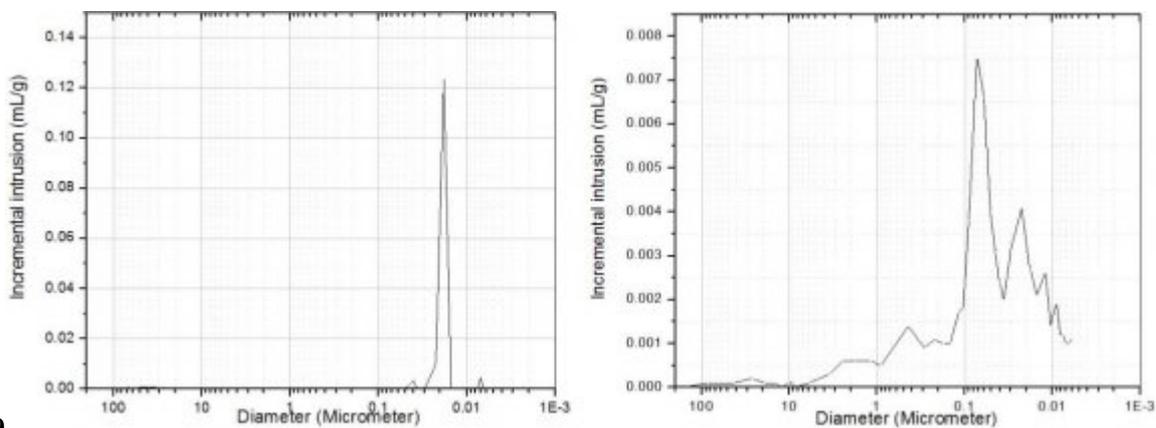

89

Figure 9: Fig. 8 :Fig. 9 :

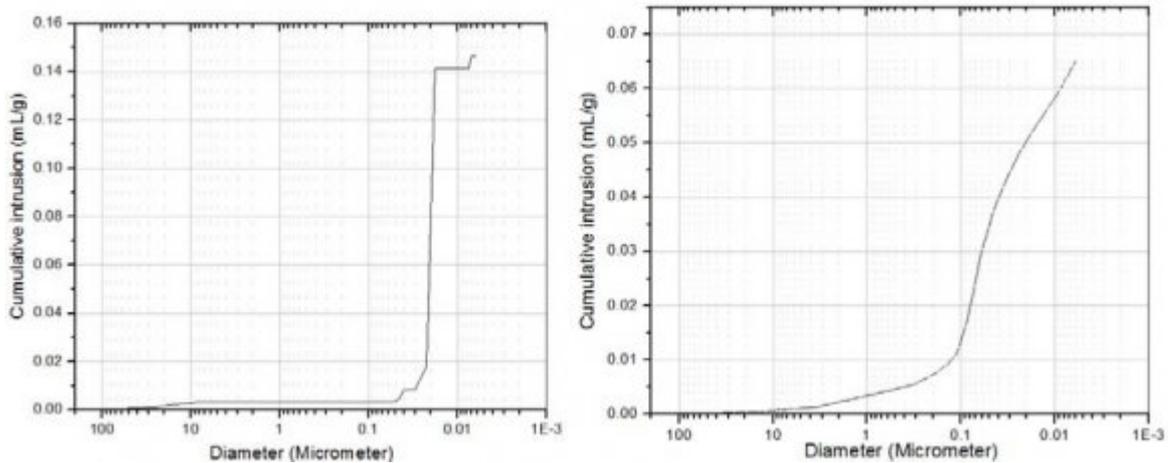


Figure 10: Fascinating

2

MWCNTs	20-55	98.31	0.0494	97
MnFe 2 O 4	49	27.28	0.0134	98-99

[Note: diameter/nm Average surface area /(m<sup>2</sup>/g) Average volume /(cc/g) Purity/% Global Journal of Researches in Engineering]

Figure 11: Table 2 : Properties of MWCNTs and MnFe 2 O 4 nanoparticles Average

3

Appearance	Colour	Specific gravity /(kg/L)	Na+Ppm	Ca+Ppm
Turbid liquid	Yellow-brown	1.08±0.005	18380	4.72

Figure 12: Table 3 :

5

Sample name	pore diameter (area) of C0 and N 3-2 specimens Total intrusion volume /(mL/g)	Total pore area /(m <sup>2</sup> /g)	Median pore diameter (volume)/nm	Median pore diameter (area)/nm
C0	0.146	28.91	22.6	22.6
N 3-2	0.065	9.15	55.3	13.2

Figure 13: Table 5 :

6

and Porosity of C0 and N1 3-2 specimens					
Sample	Average pore diameter/nm	Bulk density/(g/mL)	Apparent (skeletal) density/(g/mL)	porosity/%	
C0	20.3	2.48	3.89	36.32	
N 3-2	28.4	2.17	2.53	16.00	

Figure 14: Table 6 :

Figure 15:

- 146 [Nazari and Riahi ()] ‘Al<sub>2</sub>O<sub>3</sub> nanoparticles in concrete and different curing media’. Ali Nazari , Shadi Riahi .  
147 *Energy and Buildings* 2011. 43 p. .
- 148 [Tyson et al. ()] ‘Carbon Nanotubes and Carbon Nanofibers for Enhancing the Mechanical Properties of  
149 Nanocomposite Cementitious Materials’. B Tyson , R Al-Rub , A Yazdanbakhsh , Z Grasley . *J. Mater.*  
150 *Civ. Eng* 2011. (7) p. .
- 151 [Tanaka and Kurumisawa ()] ‘Development of technique for observing pores in hardened cement paste’. K  
152 Tanaka , K Kurumisawa . *Cem. Concr. Res* 2002. p. 1435.
- 153 [Liu et al. ()] *Effect of Nano-CaCO<sub>3</sub> on Properties of Cement Paste*, X Liu , L Chen , A Liu , X Wang . 2012.  
154 *Energy Procedia*. 16 p. .
- 155 [Meng et al. ()] ‘Effect of nano-TiO<sub>2</sub> on the mechanical properties of cement mortar’. T Meng , Yachao Yu , X  
156 Qian , S Zhan , K Qian . *Construction and Building Materials* 2012. 29 p. .
- 157 [Nazari and Riahi ()] ‘Effects of CuO nanoparticles on compressive strength of self-compacting concrete’. Ali  
158 Nazari , Shadi Riahi . *J. Indian Academy of Sciences* 2011. 36 (3) p. .
- 159 [Ahmed and Bishay ()] ‘El-dek, Magnetoelectric characteristics of Dy<sub>2.8</sub> Sr<sub>0.2</sub> Fe<sub>5</sub> O<sub>12</sub> garnet (DySrIG)’. M  
160 A Ahmed , S T Bishay , SI . *The European Physical Journal Applied Physics* 2012. (2) p. 59.
- 161 [Ahmed and Okasha ()] ‘El-Dek, Preparation and characterization of nanometric Mn ferrite via different  
162 methods’. M A Ahmed , N Okasha , SI . *Nanotechnology* 2008, 19, 6.
- 163 [Morsy and Alsayed ()] ‘Hybrid effect of carbon nanotube and nano-clay on physicomechanical properties of  
164 cement mortar’. M S Morsy , S H Alsayed , M . *Construction and Building Materials* 2011. 25 p. .
- 165 [Rafieipoura et al. ()] ‘Improvement Compressive Strength of Cementitious Composites in Different Curing  
166 Media by Incorporating ZrO<sub>2</sub> Nanoparticles’. Mohammad Rafieipoura , Ali Nazarib , Mohammad Mohandesia  
167 , Gholamreza Khalajb . *J. Materials Research* 2011.
- 168 [Shekaria and Razzaghib ()] ‘Influence of nano particles on durability and mechanical properties of high  
169 performance concrete’. A H Shekaria , M S Razzaghib . *British Standard Institution, BS* 2011. 1996. 14  
170 p. . Specifications for Portland Cement., BSI (J. Procedia Engineering)
- 171 [Kong et al. ()] ‘Influence of nano-silica agglomeration on microstructure and properties of the hardened cement-  
172 based materials’. Deyu Kong , Xiangfei Du , Su Wei , Hua Zhang , P Shah . *Construction and Building*  
173 *Materials* 2012. 37 p. .
- 174 [Abell et al. ()] ‘Mercury Intrusion Porosimetry and Image Analysis of Cement-Based Materials’. A Abell , K  
175 Willis , D Lange . *J. Colloid Interface Sci* 1999. p. 39.
- 176 [Grebler and Gazso ()] *Nano in the Construction Industry, Nano Trust Dossiers-Institute of Technology Assess-*  
177 *ment of the Austrian Academy of Sciences*, S Grebler , A Gazso . 2012. 32 p. .
- 178 [Al-Salami et al. ()] *The effect of curing time and porosity on the microstructure hydrated products in some*  
179 *blended cement pastes, Silicate Industrial*, A E Al-Salami , M S Al , - Assiri , A Al-Hajry , M A Ahmed , S  
180 Taha . 2007. 72 p. 163.
- 181 [Nazari et al. ()] ‘The effects of incorporation Fe<sub>2</sub>O<sub>3</sub> nanoparticles on tensile and flexural strength of concrete’.  
182 A Nazari , S Riahi , S Shamekhi , A Khademno . *J. Amer. Sci* 2010. 6 (4) p. .
- 183 [Nazari and Riahi ()] ‘The effects of zinc dioxide nanoparticles on flexural strength of selfcompacting Concrete’.  
184 Ali Nazari , Shadi Riahi . *J. Composites B* 2011. 42 p. .
- 185 [Yazdi et al. ()] ‘to study the effect of adding Fe<sub>2</sub>O<sub>3</sub> nanoparticles on the morphology properties and  
186 microstructure of cement mortar’. N Yazdi , M Arefi , E Mollaahmadi , B Nejand . *Life Science Journal*  
187 2011. 8 (4) .
- 188 [Zhang et al. ()] ‘Use of nano-silica to increase early strength and reduce setting time of concretes with high  
189 volumes of slag’. M.-H Zhang , J Islam , S Peethamparan . *Cement & Concrete Composites* 2012. 34 p. .