

Effects of Simulation Parameters on Residual Stresses in 3D Finite Element Laser Shock Peening Analysis

Ju Hee Kim¹

¹ Dept. of Mechanical Engineering/Korea Military Academy

Received: 13 December 2012 Accepted: 5 January 2013 Published: 15 January 2013

Abstract

Laser shock peening(LSP) is an innovative surface treatment technique, which is successfully applied to improve fatigue performance of metallic components. After the treatment, the fatigue strength and fatigue life of a metallic material can be increased remarkably owing to the presence of compressive residual stresses in the material. Recently, the incidences of cracking in Alloy 600 small-caliber penetration nozzles (CRDM (control rod drive mechanism) and BMI(bottom mounted instrument)) have increased significantly. The cracking mechanism has been attributed to primary water stress corrosion cracking (PWSCC) and has been shown to be driven by welding residual stresses and operational stresses in the weld region. For this reason, to mitigating weld residual stress, preventive maintenance of BMI nozzles was considered application of laser shock peening process. Effects of parameters related to finite element simulation of laser shock peening process to determine residual stresses are discussed, in particular parameters associated with the LSP process, such as the maximum pressure, pressure pulse duration, laser spot size and number of shots. It is found that certain ranges of the maximum pressure and pulse duration can produce maximum compressive residual stresses near the surface, and thus proper choices of these parameters are important. For the laser spot size, residual stresses are not affected, provided it is larger than a certain size. Magnitudes of compressive residual stresses are found to increase with increasing number of shots, but the effect is less pronounced for more shots.

Index terms— FE analysis, LSP (laser shock peening), residual stress.

1 Effects of Simulation Parameters on Residual

Stresses in 3D Finite Element Laser Shock Peening Analysis

Abstract-Laser shock peening (LSP) is an innovative surface treatment technique, which is successfully applied to improve fatigue performance of metallic components. After the treatment, the fatigue strength and fatigue life of a metallic material can be increased remarkably owing to the presence of compressive residual stresses in the material. Recently, the incidences of cracking in Alloy 600 small-caliber penetration nozzles (CRDM (control rod drive mechanism) and BMI (bottom mounted instrument)) have increased significantly.

The cracking mechanism has been attributed to primary water stress corrosion cracking (PWSCC) and has been shown to be driven by welding residual stresses and operational stresses in the weld region. For this reason, to mitigating weld residual stress, preventive maintenance of BMI nozzles was considered application of laser shock peening process. Effects of parameters related to finite element simulation of laser shock peening process to determine residual stresses are discussed, in particular parameters associated with the LSP process, such as the maximum pressure, pressure pulse duration, laser spot size and number of shots. It is found that certain ranges of the maximum pressure and pulse duration can produce maximum compressive residual stresses near

the surface, and thus proper choices of these parameters are important. For the laser spot size, residual stresses are not affected, provided it is larger than a certain size. Magnitudes of compressive residual stresses are found to increase with increasing number of shots, but the effect is less pronounced for more shots.

Keywords: FE analysis, LSP (laser shock peening), residual stress.

2 Introduction

Laser shock peening (LSP) is an innovative surface treatment technique, producing compressive residual stresses near the surface and thus improving fatigue performance of metallic components [1,2]. Through the LSP processing, the surface of the metallic target is exposed to an intense laser beam with high density (in the GW/cm² range) for short duration (tens of nanoseconds). The thermo-protective coating (black paint or taping) is vaporized because of the highenergy laser pulse, forming a plasma that reaches temperatures in excess of 10,000 °C. An extremely high pressure (the order of GPa) on the metal surface is generated bythe extremely rapid expansion of the heated plasma [1][2][3]. The high pressure then propagatesinto the material interior. As a result, plastic deformation occurs and a hardened layer is formed on the surface of the metallic target, enhancing mechanical properties such as hardness, fatigue strength, and stress corrosion cracking resistance.

In the present work, effects of parameters related to finite element (FE) simulation of LSP process to determine residual stresses is discussed. Simulations were performed using the general purpose FE program ABAQUS [4].

3 II.

4 F Analysis a) Simulation Procedures

As the LSP process involves high speed impact and dynamic wave propagation, explicit time integration FE codes need to be employed, for instance, using the ABAQUS/Explicit code [4]. There can be two approaches to simulate the LSP process. The first approach is to use explicit time integration FE codes only(procedure ?). Although this approach is relatively easy to perform, it requires long computation times. This is because calculation times should be chosen to be sufficiently long, as full development of plastic deformation in the material during the LSP process takes much longer than the duration of the pulse pressure, due to reflection and interaction of shock waves propagating in the target.

The second, more efficient, approach is to combine ABAQUS/Explicit and ABAQUS/Implicit codes (procedure ?). In this approach, dynamic analysis is firstly performed using the ABAQUS/Explicit code. When the dynamic analysis is completed, the deformed element data with all transient stresses and strains information are then imported into the ABAQUS/Implicit code to calculate residual stress fields using static analysis. For cases considered in this paper, it is found that the above two approaches give the same results, and thus the latter (and more efficient) approach is used throughout the paper.

5 b) Modeling Pressure Loading

Assuming a constant absorbed laser power density I_0 in the confined ablation mode, the maximum peak pressure induced by plasma, P_{max} , is given by [1,2,[5][6][7] (1)

where η is the efficiency of the interaction; and Z is the reduced shock impedance between the material and the confining layer [1,8].

(
Although the pressure-time history for simulating LSP is usually described using a Gaussian temporal profile, it is in fact very close to a triangular ramp because of very short pressure pulse duration (order of 100ns), as shown in Fig. ???. Thus, in this wo rk, the pressure is assumed to increase linearly to the maximum pressure, P_{max} , and then decrease linearly for a total pulse duration, $2t_p$, as shown in Fig. ??.

6 c) Modeling Plastic Deformation Due to Shock Wave

As the shock wave propagates into the metal, plastic deformation occurs up to a depth at which the peak stress equals the Hugoniot elastic limit (HEL) of the material. The HEL is related to the dynamic yield strength at high strain rates, $\sigma_{y,d}$, according to [1,2,[5][6][7][8] (3) where ν is Poisson's ratio.

7 III.

8 Sensitivity Analysis for LSP Simulation a) Geometry and FE mesh

As a generic problem, the present work considers one-sided laser peening on an infinite plate. The impact zone is assumed to be rectangular with a half-length x_p , as schematically shown in Fig. ??a.

Corresponding three-dimensional (3D) FE quarter model is shown in Fig. ??b. The FE analysis domain has a halflength x_f (which is fixed to $x_f = 5$ mm in this work).

Outside the domain, infinite elements are used to simulate an infinite plate. For the element type, the first order elements (C3D8R for finite elements and CIN3D8 for infinite elements within ABAQUS) are used.

9 b) Material Properties

The material is assumed to be the 35CD4 50HRC steel alloy, of which physical and mechanical properties, taken from Ref. [1], are given in Table ???. Other parameters used in simulations are; c) Parameters for Sensitivity Analysis

10 d) Validation

Before presenting results of sensitivity analysis, the present analysis is validated by comparing with existing experimental data [9]. The material was the 35CD4 50HRC steel alloy that is the same as the one considered in the present work. Laser peening parameters (P_{max} , t_d , x_p and n) were the same as the reference values given in Table 2. More detailed information on experiments can be found in Ref. [9].

Simulated residual stresses are compared with experimental results in Fig. 4. Figure 4a compares variations of σ_x and σ_y residual stresses in the surface (at $y=z=0$) with distance x . Variations of σ_x and σ_y residual stresses with depth z (at $x=y=0$) are compared in Fig. 4b. Experimental data show that both residual stresses, σ_x and σ_y , are similar. Despite differences between experimental and simulated residual stresses, overall trends in experimental data can be 1 Note that reference values for P_{max} , t_d , x_p and n were chosen to max (GPa) 0.01 23 o P Z I ? ? ? 1 2 2 1 1 Z Z Z ? ? (1) (1 2) d y HEL ? ? ? ? ? ?

compare with existing experimental data, as will be described in the next subsection captured by simulation.

There are many parameters possibly affecting FE simulation results of the LSP process. They can be broadly categorized into two groups. The first group includes parameters associated with dynamic FE analysis, such as the mesh size Le , solution time for dynamic analysis, t_s , time step, Δt and dynamic yield strength, $\sigma_y d$. The other group includes parameters associated with the LSP process, such as the maximum pressure, P_{max} , pressure pulse duration, t_d , laser spot size, r_p and the number of shots, n . For sensitivity analysis, the reference values for these variables are chosen, as given in Table 2.1 Each variable is then systematically varied to see its effect on simulation results. $\sigma=0.1$, $Z1=3.6$ 106(g/cm-2s-1) and $Z2=0.165$ 106(g/cm-2s-1) [1,8] IV.

11 Sensitivity Analysis Results

12 a) Effect of the Mesh Size

It is known that FE LSP simulation results are not affected by the element size, provided it is less than about 5% of the spot size, x_p [1, 5]. The critical element size is 125 problem. To see the effect of the mesh size, three different FE models were prepared, having the element size ranging from $Le=100 \mu m$ to $Le=250 \mu m$, and results are shown in Fig. ???. In Fig. ?? as well as in subsequent figures, two residual stress profiles are presented. The first one is variations of the σ_x residual stresses at the surface ($y=z=0$) with distance x , shown in Fig. ??a. The second result is variations of the σ_x residual stresses at the center of the laser spot ($x=y=0$) with depth z , shown in Fig. ??b.

Results in Fig. ?? confirm the existing finding that simulated residual stresses are not affected when the element size is less than 5% of the spot size, x_p .

13 b) Time Step for Stability

In dynamic analysis, the time step, Δt , should be chosen to be smaller than the stability limit for numerical stability. The stability limit can be estimated from [1,10,11] (4)

where Le denotes the smallest element size; C_d is the wave speed of material; E is Young's modulus; and ρ is the mass density. For the present problem, $C_d= 5.193 \times 10^3$ m/s with $Le=125 \mu m$ gives $\Delta t=5.78$ ns. For the sake of space, results are not shown but simulated residual stress results are found not to be affected by the time step, provided that it is less than Δt , given by Eq.(4).

14 c) Solution time for dynamic analysis (t_s)

To obtain residual stress fields due to dynamic wave propagation by LSP, the solution time in dynamic analysis must be taken much longer than the laser duration time. Figure ?? shows dynamic stress profiles at four different times during dynamic analysis. Results show that simulated dynamic stress profiles are affected by t_s .

After $t_s=2,000$ ns, the dynamic stress profile in the depth direction gradually becomes steady, but the dynamic stress profile at surface become steady only after $t_s=5,000$ ns. Results suggest that the solution time for dynamic analysis should be chosen to be larger than 5,000ns, which is about hundred times larger than the pulse duration $t_d=50$ ns.

15 Dynamic Yield Strength ($\sigma_y d$)

As the strain rate during the LSP process is faster than 10^{-6} s $^{-1}$, plastic deformation is determined by the dynamic yield strength, $\sigma_y d$. As information on $\sigma_y d$ may have uncertainty, the effect of $\sigma_y d$ is investigated by varying $\sigma_y d$ from 1.0GPa to 1.5GPa, and the results are shown in Fig. 8. Results show that magnitudes of compressive residual stresses decrease almost linearly with increasing $\sigma_y d$, due to the fact that increasing

19 CONCLUSIONS

the material yield strength tends to increase material resistance against plastic deformation [11]. e) Maximum Pressure (P_{max} , see Fig. ??)

The plasma pressure pulse induced by LSP depends on the laser power density, as shown in Eq. (1). Increasing laser power density increases the magnitude of the pressure pulse on the material surface. The plastic deformation in the material depends mainly on the HEL. No plastic deformation occurs in the material for $P_{max} < HEL$. The plastic strain occurs with a purely elastic reverse strain for $HEL < P_{max} < 2 \times HEL$, and the plastic strain fully occurs for $P_{max} > 2 \times HEL$ [1,2,6].

To see the effect of the laser power density on residual stresses, simulations are performed for P_{max} , ranging from 2.5GPa to 5GPa, and results are shown in Fig. ???. Note $HEL = 2.1GPa$ for the present problem.

Results show that magnitudes of compressive residual stresses near the surface increase with increasing P_{max} up to $P_{max} = 4GPa$. For $P_{max} = 5GPa$, the magnitudes of compressive residual stresses in the surface are overall smaller than those for $P_{max} = 4GPa$.

Along the depth direction, the plastically affected zone size increases with increasing P_{max} . For $P_{max} = 2.5GPa$ and 3GPa, magnitudes of compressive residual stresses decrease monotonically. However, for $P_{max} = 4GPa$ and 5GPa, they increase near the surface and then decrease. Results in Fig. ??? suggest that the case of $P_{max} = 4GPa$ can produce optimum laser peening treatment, which is fully consistent to the existing finding that materials can be optimally treated with $P_{max} = (2-2.5) \times HEL$ range [1,6]. Results show that the choice of the laser power density is important in the LSP process to produce desired residual stress profiles.

f) Pressure Duration (td)

In addition to the laser power density, the pressure duration is another important parameter associated with the LSP process. Figure ??? shows the 3D profile of predicted residual stresses (von Mises stress) on the surface and in the depth directions, impacted at a spot size of $x_p = 2.5mm$. measurement, results in Fig. 4 suggest that FE simulation of the LSP process is reliable. Figure ?? effect of the pressure duration of laser pulse on residual stresses decrease monotonically with the depth. For $td = 100ns$, they increase near the surface and then decrease. For larger td , such trend is more pronounced. Results in Fig. ??? suggest that the pressure duration should be chosen properly to obtain desired residual stress profiles.

16 g) Laser Spot Size (x_p)

To see the effect of the laser spot size, simulations are performed for various laser spot sizes (r_p) ranging from 0.5mm to 2.5mm, with the fixed $P_{max} = 3GPa$ and pulse duration of $td = 50ns$, and results are shown in Fig. ???1. The affected zone size of compressive residual stresses in the surface obviously increases with increasing laser spot size. However, residual stresses in the depth direction are not affected by the laser spot size, provided it is larger than 1.5mm.

17 h) Number of Shots (n)

In practice, the multiple LSP process can be performed to produce more compressive residual stresses. The effect of multiple LSP process (from single to four times) on simulated residual stresses is shown in Fig. ???2. In simulation, the parameters associated with the LSP process are fixed; $P_{max} = 3GPa$, $x_p = 2.5mm$ and $td = 50ns$. Multiple LSP is applied to the same area.

Results show that magnitudes of compressive residual stresses increase with increasing number of shots, but the effect on residual stresses is less pronounced for more shots.

18 i) FE results using LSP optimal process parameters

The surface and depth residual stress distributions resulting from the optimum parameters of LSP system are shown in Fig. ???3. Then optimum LSP parameters such as peak pressure ($2 \times HEL = 4.2GPa$), laser spot size (2.5mm), and laser pulse duration (100ns) are used in same conditions. As shown in Fig. ???3a, after one impact using optimum LSP parameters on same area, the surface residual stresses have increased remarkably. It shows that the maximum compressive residual stresses increase to about 567MPa, which is 62% higher than that for $P_{max} = 3GPa$, $td = 50ns$. The distributions of the depth residual stresses plotted in Fig. ???3b. Along the depth direction, the plastically affected zone size (L_p) decreases to about 1.42mm, which is 136% higher than that for $P_{max} = 3GPa$, $td = 50ns$. Therefore, residual stresses due to the LSP optimal process parameters result in a more effective residual stress.

V.

19 Conclusions

In the present work, effects of parameters related to finite element (FE) simulation of LSP process to determine residual stresses are discussed. Two groups of parameters are considered: one those associated with dynamic FE analysis, such as the mesh size, solution time for dynamic analysis, time step and dynamic yield strength; and the other associated with the LSP process, such as the maximum pressure, pressure pulse duration, laser spot size and number of shots.

Conclusions can be summarized as follows. ? The mesh size should be chosen to be smaller than 5% of the spot size. ? The solution time for dynamic analysis should be chosen to be sufficiently long, about hundred

times larger than the pulse duration. ? The effect of the dynamic yield strength on simulated residual stresses is almost linear. ? Certain ranges of the maximum pressure and pulse duration can produce maximum compressive residual stresses near the surface, and thus proper choices of these parameters are important. ? Residual stresses in the depth direction are not affected by the laser spot size, when it is larger than a certain size. ? Magnitudes of compressive residual stresses increase with increasing number of shots, but the effect is less pronounced for more shots.

However, for $t_d = 100\text{ns}$, residual stresses near the center become less compressive. For $t_d = 150\text{ns}$, they can be even tensile. Along the depth direction, the plastically affected zone size increases with increasing t_d . For $t_d = 30\text{ns}$ and 50ns , magnitudes of compressive simulated residual stresses. In the surface, residual stress profiles for $t_d = 30\text{ns}$ and 50ns are similar.


and Quantum Electronics, Vol. 27, pp. 1213-1229, 1995. Table ?? : Mechanical properties of the 35CD4 50HRC steel alloy [1] Global Journal of Researches in Engineering

20 Volume XIII Issue IX Version I ()

A Year




Figure 1: Figure 1 :Figure 2 :Figure 3 :

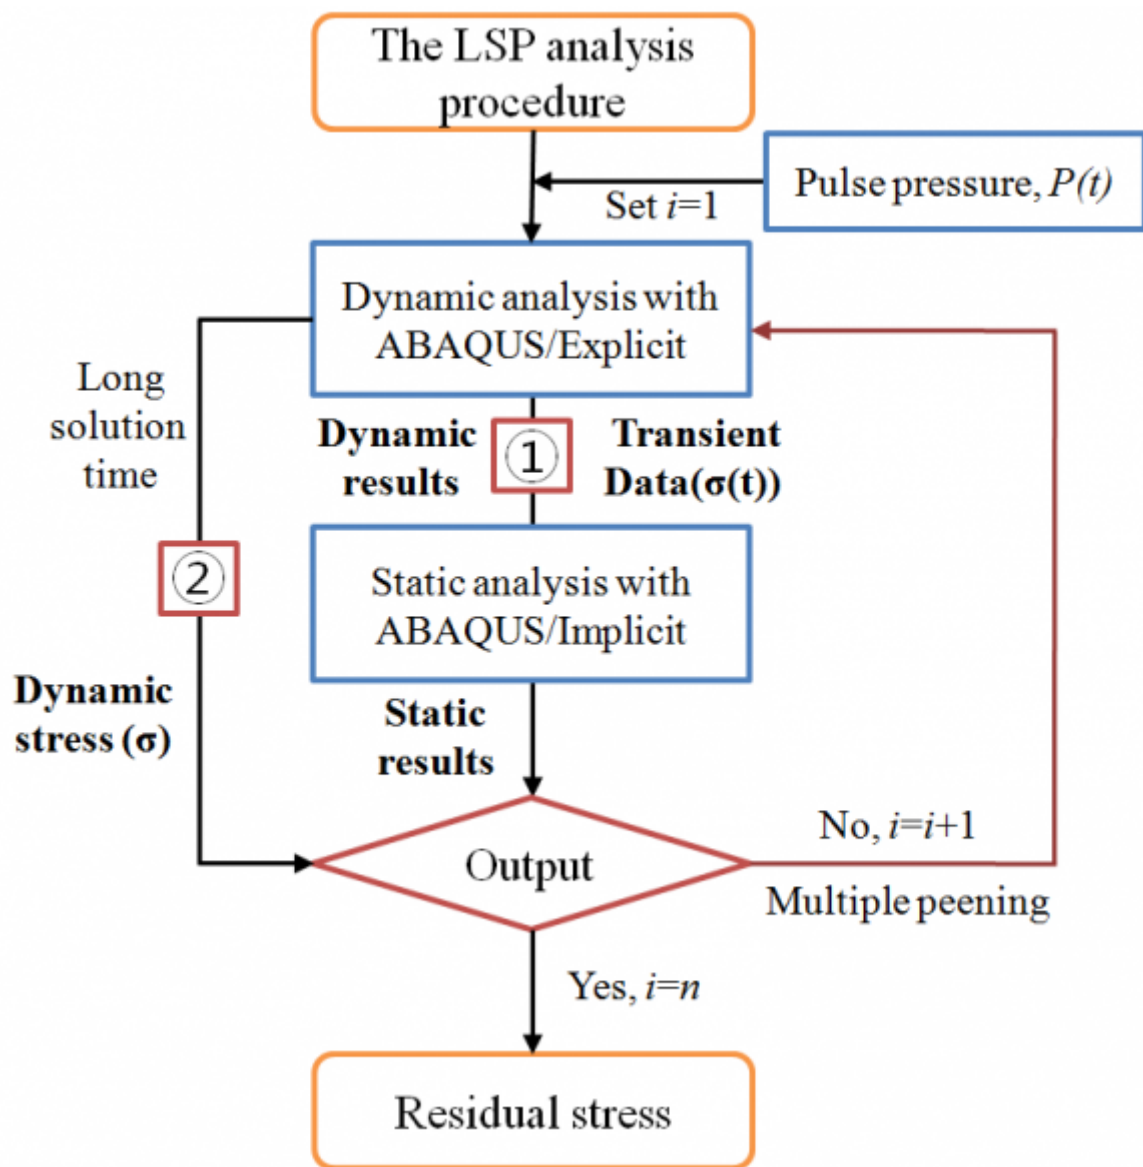


4

Figure 2: Figure 4 :

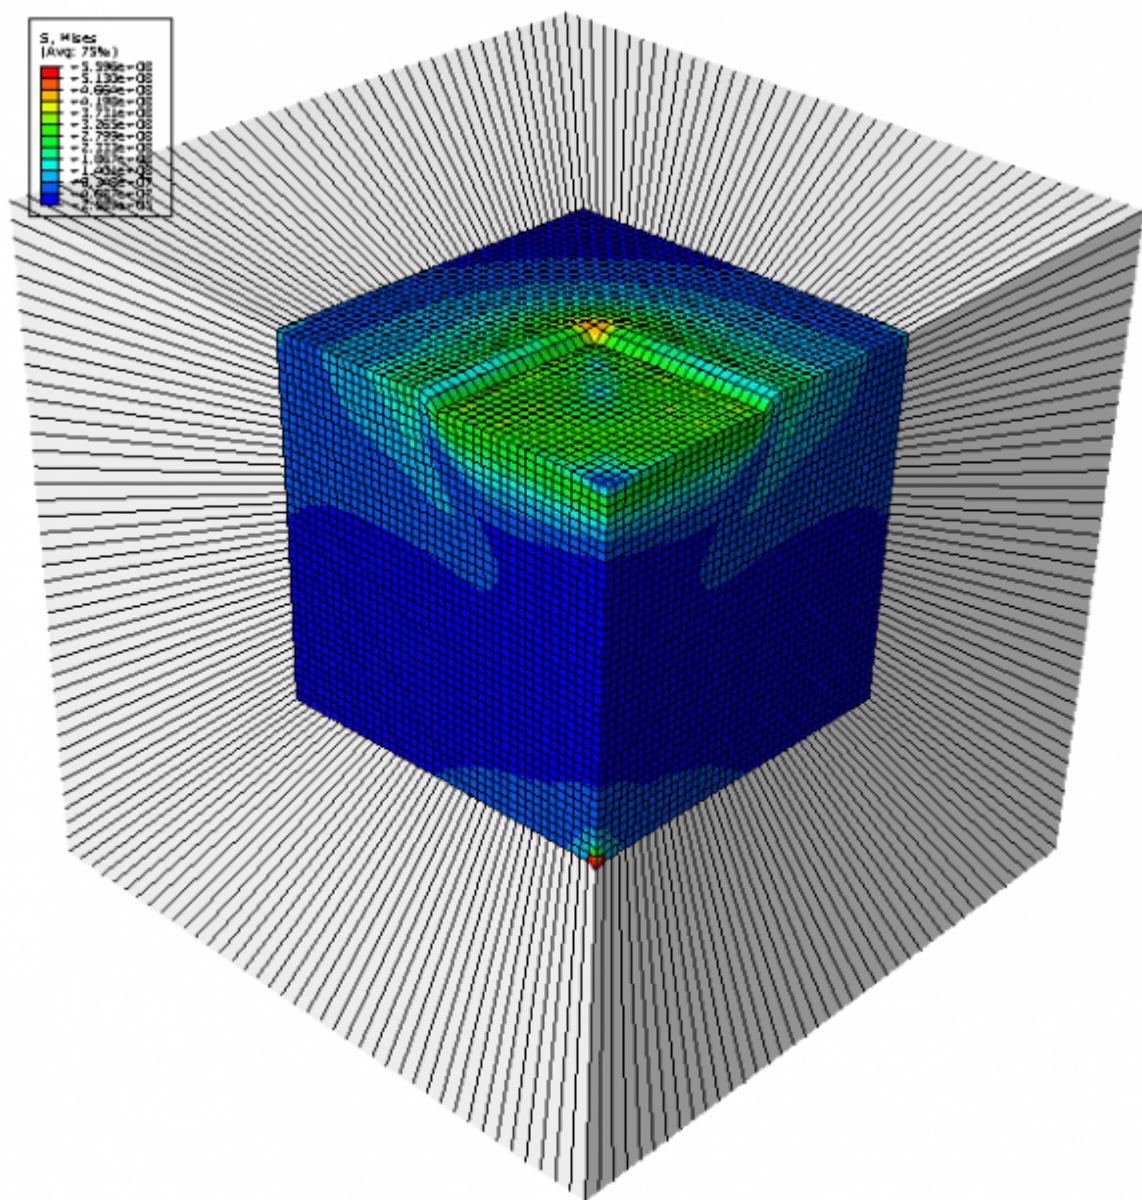


567

Figure 3: Figure 5 :Figure 6 :Figure 7 :

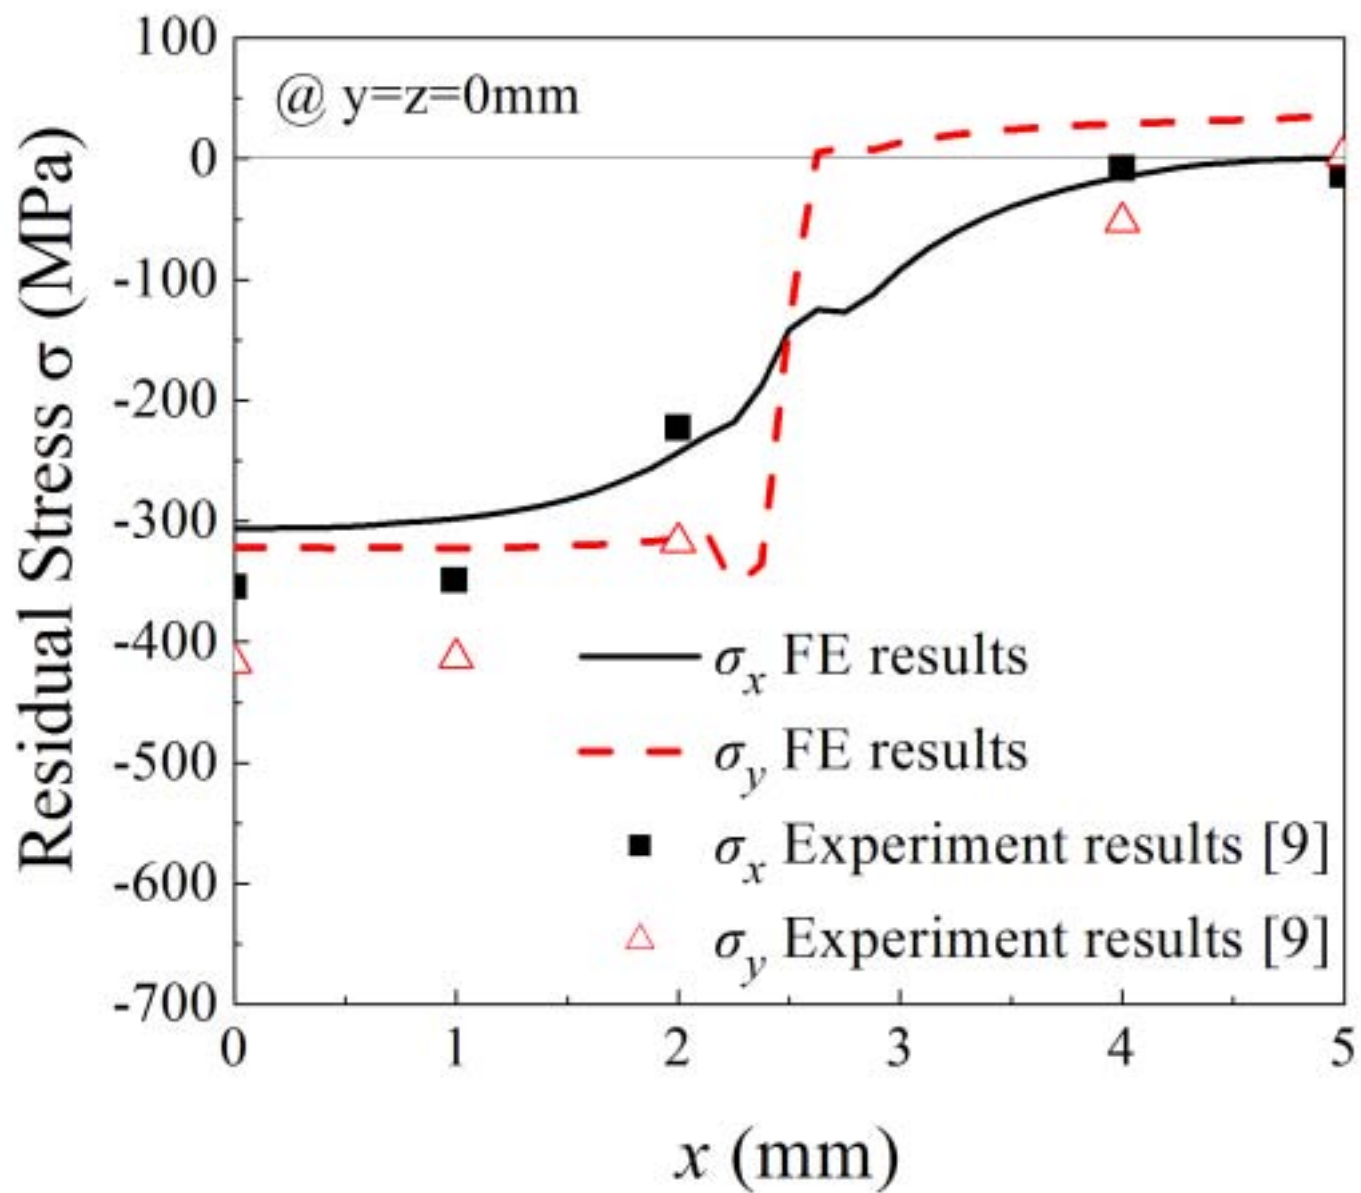


8

Figure 4: Figure 8 :

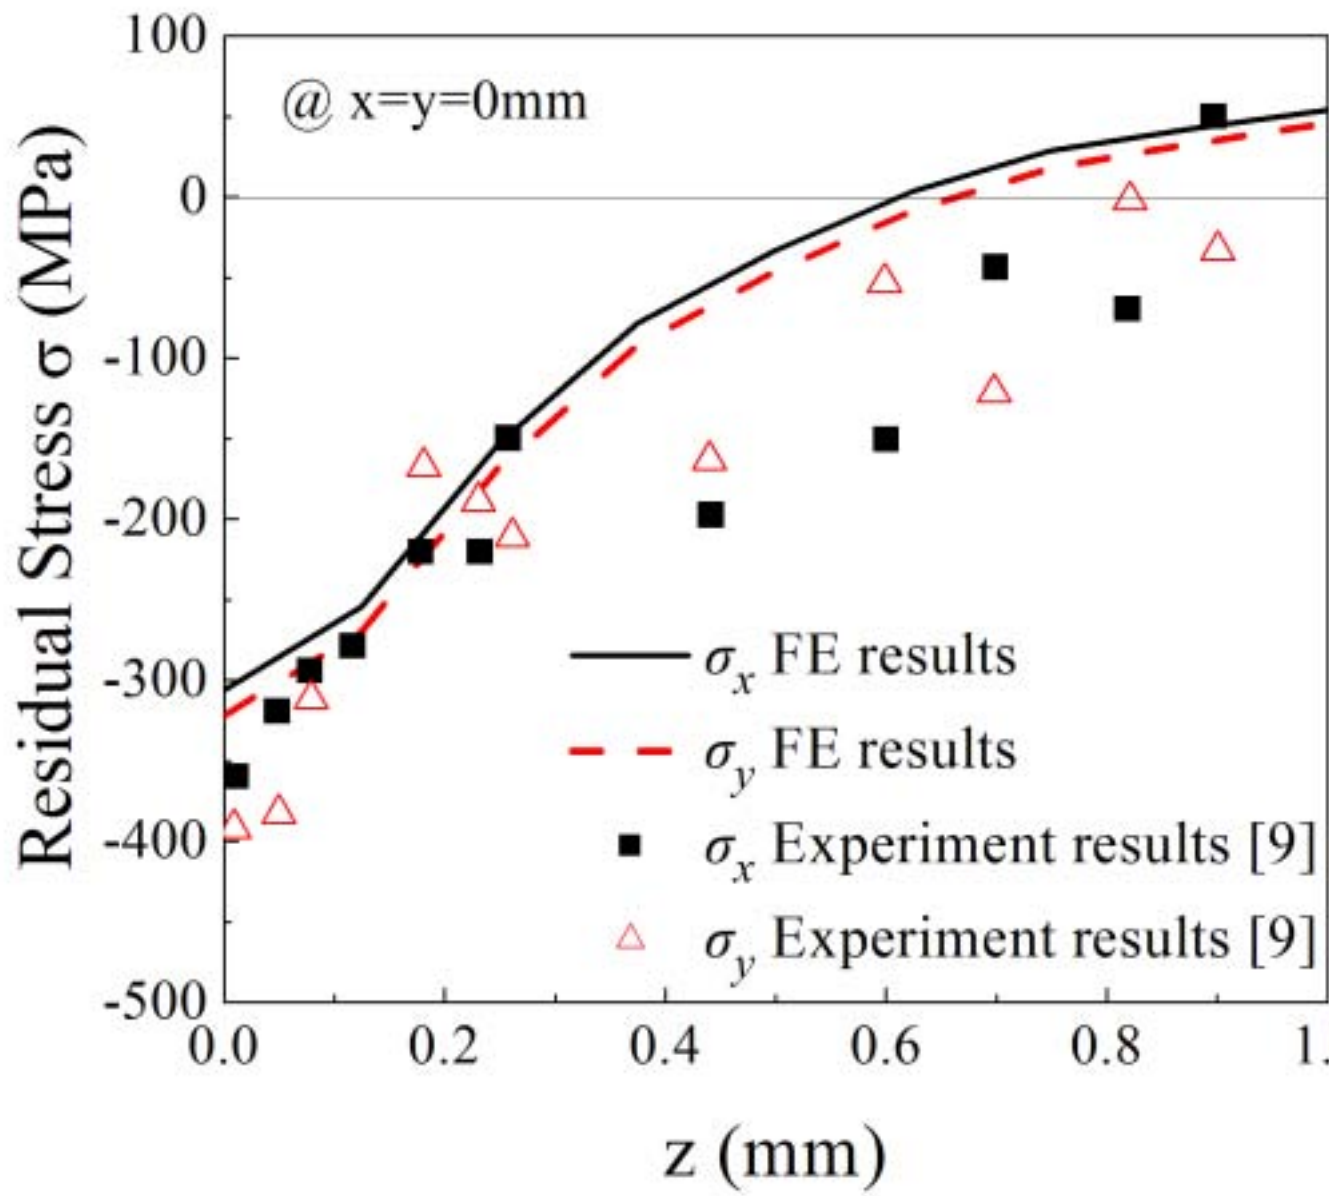

910

Figure 5: Figure 9 :Figure 10 :

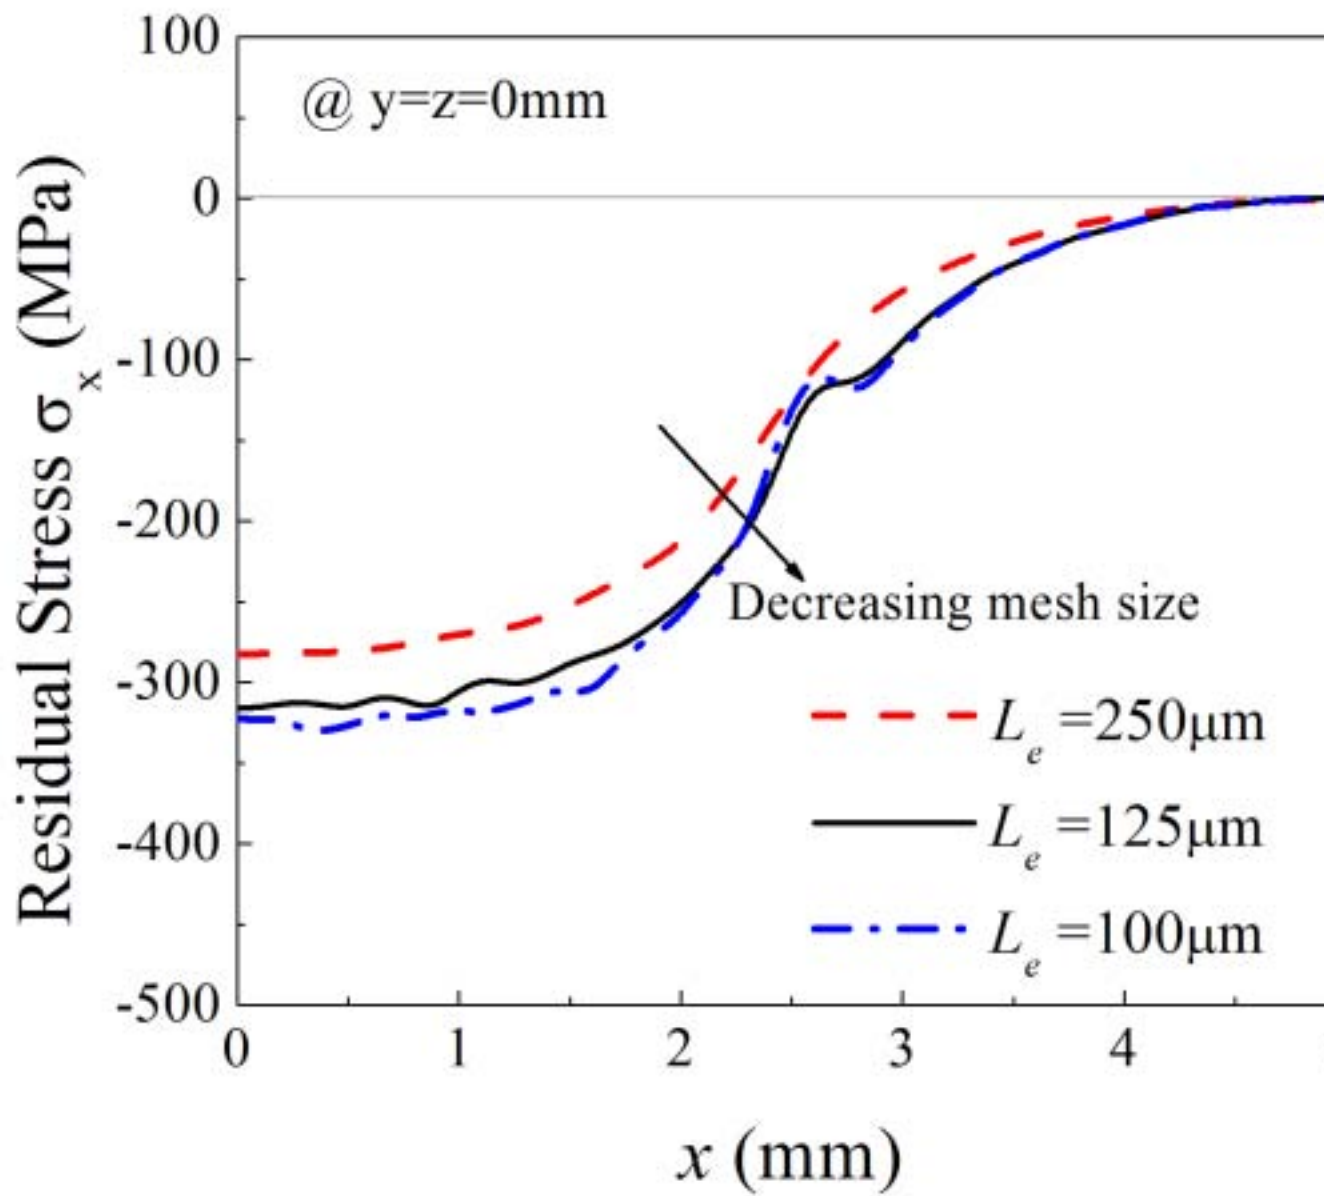

1112

Figure 6: Figure 11 :Figure 12 :

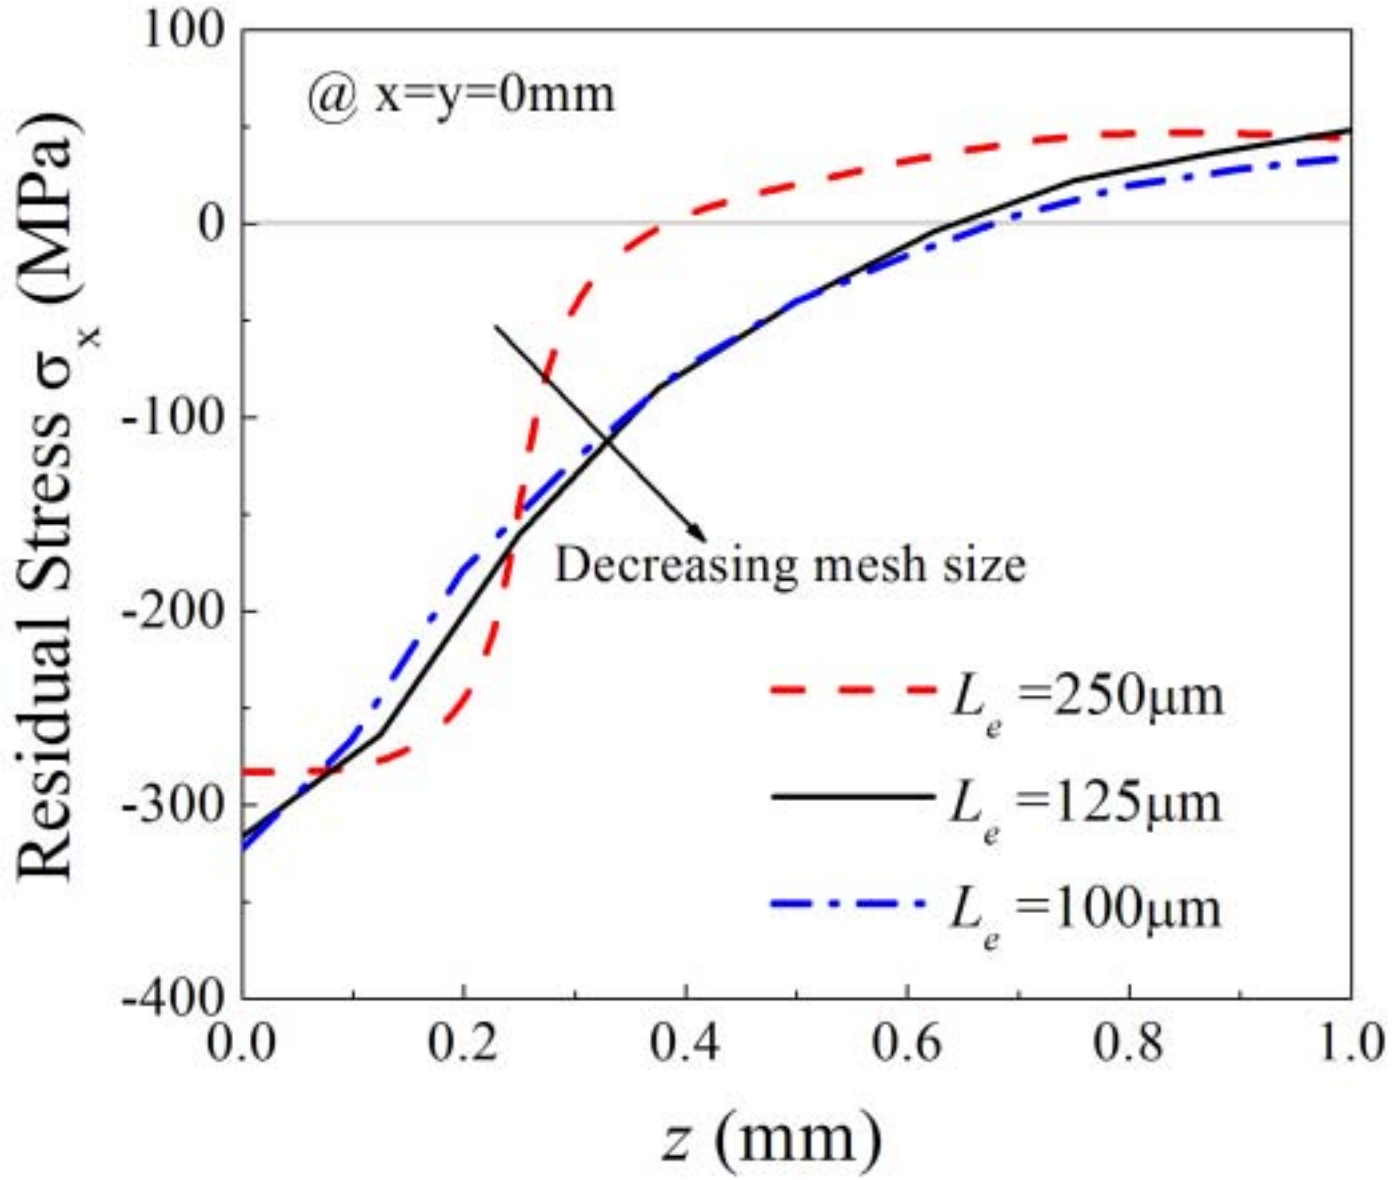


Figure 7:

2

Parameter	Ref.	Ranges
Mesh size, L_e (mm)	0.125	0.25-0.1
Solution time for dynamic analysis, t_p (ns)	5,000	500-5,000
Dynamic yield strength, σ_y	d 1.24 (GPa)	1-1.5
Maximum pressure, P_{max} (GPa)	3	2.5-5
Pressure pulse duration, t_d (ns)	50	30-150
Laser spot size, x_p (mm)	2.5	0.5-2.5
Number of shots, n (shot)	1	1-4

Figure 8: Table 2 :

.1 ()

This page is intentionally left blank This page is intentionally left blank

- [Braisted and Brockman ()] ‘Finite element simulation of laser shock peening’. W Braisted , R Brockman . *Int. J. of Fatigue* 1999. 21 p. .
- [Yang et al. ()] ‘Geometrical effects on residual stresses in 7050-T7451 aluminum alloy rods subject to laser shock peening’. C Yang , P D Hodgso , Q Liu , L Ye . *J. of Material Processing Technology* 2008. 201 p. .
- [Ling et al. ()] ‘Influence of Laser Peening Parameters on Residual Stress. Field of 304 Stainless Steel’. X Ling , W Peng , G Ma . *J. of Pressure Vessel Technology* 2008. 130 (021120) p. .
- [Masse and Barreau ()] ‘Laser generation of stress waves in metal’. J E Masse , G Barreau . *Surface and Coating Technology* 1995. 70 p. .
- [Ding and Ye ()] *Laser shock peening Performance and process simulation*, K Ding , L Ye . 2006. CRC Press. p. .
- [Peyre and Fabbro] *Laser shock processing: a review of the physics and applications*, P Peyre , R Fabbro . (Optical)
- [Hu and Yao ()] ‘Numerical simulation and experimentation of overlapping laser shock processing with symmetry cell’. Y Hu , Z Yao . *Int. J. of Machine Tools & Manufacture* 2008. 48 p. .
- [Bang et al. ()] ‘Residual Stress Prediction in LSP Surface Treatment by Using FEM’. B W Bang , S K Son , J M Kim , C D Cho . *KSME-A* 2009. 33 (8) p. .
- [Ballard et al. ()] ‘Residual stresses induced by laser-shocks’. P Ballard , J Fournier , R Fabbro , J Frelat . *J. de Physique IV* 1991. 1 p. .
- [Ding and Ye ()] ‘Simulation of multiple laser shock peening of a 35CD4 steel alloy’. K Ding , L Ye . *J. of Materials Processing Technology* 2006. 178 p. .
- [User’s manual, Dassault Systemes ABAQUS Version 6.7 and 6 ()] ‘User’s manual, Dassault Systemes’. *ABAQUS Version 6.7 and 6*, 2008. 9.